

Electronic theory for superconductivity in Sr_2RuO_4 : triplet pairing due to spin-fluctuation exchange

I. Eremin^{1,2}, D. Manske¹, C. Joas¹, and K.H. Bennemann¹

¹*Institut für Theoretische Physik, Freie Universität Berlin, D-14195 Berlin, Germany*

²*Physics Department, Kazan State University, 420008 Kazan, Russia*

(February 6, 2001)

Using a two-dimensional Hubbard Hamiltonian for the three electronic bands crossing the Fermi level in Sr_2RuO_4 we calculate the band structure and spin susceptibility $\chi(\mathbf{q}, \omega)$ in quantitative agreement with nuclear magnetic resonance (NMR) and inelastic neutron scattering (INS) experiments. The susceptibility has two peaks at $\mathbf{Q}_i = (2\pi/3, 2\pi/3)$ due to the nesting Fermi surface properties and at $\mathbf{q}_i = (0.6\pi, 0)$ due to the tendency towards ferromagnetism. Applying spin-fluctuation exchange theory as in layered cuprates we determine from $\chi(\mathbf{q}, \omega)$, electronic dispersions, and Fermi surface topology that superconductivity in Sr_2RuO_4 consists of triplet pairing. Combining the Fermi surface topology and the results for $\chi(\mathbf{q}, \omega)$ we can exclude s - and d -wave symmetry for the superconducting order parameter. Furthermore, within our analysis and approximations we find that f -wave symmetry is slightly favored over p -wave symmetry due to the nesting properties of the Fermi surface.

74.20.Mn, 74.25.-q, 74.25.Ha

The novel spin-triplet superconductivity with $T_c=1.5\text{K}$ observed recently in layered Sr_2RuO_4 seems to be a new example of unconventional superconductivity [1]. The presence of incommensurate antiferromagnetic and ferromagnetic spin fluctuations confirmed recently by inelastic neutron scattering (INS) [2] and NMR ^{17}O Knight shift [3], respectively, suggests a pairing mechanism for Cooper-pairs due to spin fluctuations. This is further supported by the observed non s -wave symmetry of the order parameter. Likely Sr_2RuO_4 is another example of spin fluctuations induced superconductivity. This makes the theoretical investigation of ruthenates very interesting. NMR [4] and polarized neutron scattering [5] measurements indicate spin-triplet state Cooper-pairing. In analogy to ^3He this led theorists to conclude that p -wave superconductivity is present [6]. However, by fitting the specific heat and the ultrasound attenuation Dahm *et al.* doubted p -wave superconductivity [7] and propose an f -wave symmetry of the superconducting order parameter. A similar conclusion was drawn in Ref. [8]. Recently it has been reported that also thermal conductivity measurements are most consistent with f -wave symmetry [9].

Clearly, it is important to analyze more definitely the origin of superconductivity, triplet pairing and also the symmetry of the order parameter on a basis of an electronic calculation. This is difficult, since there are three $\text{Ru}^{4+} t_{2g}$ bands that cross the Fermi level with $\approx 2/3$ -filling of every band in Sr_2RuO_4 . The hybridization between all three bands seems to cause a single T_c . All bands cross the Fermi level and hence, the cross-susceptibilities are not small and play an important role. In view of these facts the previous theoretical analysis of the gap symmetries and competition between p and d -wave superconductivity [10–12] must be re-examined and it is necessary to determine superconductivity within an electronic theory and to derive the symmetry of the order

parameter from general arguments.

In this letter we present an electronic theory which takes into account the hybridization between all three bands. We calculate the Fermi surface (FS), energy dispersion and the spin susceptibility χ including *all* cross-susceptibilities. Then, we analyze the pairing interaction mediated by the spin fluctuations exchange in Sr_2RuO_4 . Analyzing experimental results for the ^{17}O Knight shift and INS data as well as the FS observed by Angle-Resolved-Photoemission-Spectroscopy (ARPES) [13] we obtain values for the hopping integrals and effective Coulomb repulsion U . Taking this as an input into the pairing interaction we analyze the p -, d - and f -wave superconducting gap symmetries. The delicate competition between weak ferromagnetic spin fluctuations and relatively strong incommensurate antiferromagnetic spin fluctuations due to nesting of the FS cause triplet Cooper-pairing. We get singlet $d_{x^2-y^2}$ -wave symmetry is energetically less favorable.

We start from the two-dimensional three-band Hubbard Hamiltonian

$$H = \sum_{\mathbf{k}, \sigma} \sum_{\alpha} t_{\mathbf{k}\alpha} a_{\mathbf{k}, \alpha \sigma}^+ a_{\mathbf{k}, \alpha \sigma} + \sum_{i, \alpha} U_{\alpha} n_{i\alpha \uparrow} n_{i\alpha \downarrow}, \quad (1)$$

where $a_{\mathbf{k}, \alpha \sigma}$ is the Fourier transform of the annihilation operator for the d_{α} orbital electrons ($\alpha = xy, yz, zx$) and U_{α} is an effective on-site Coulomb repulsion. $t_{\mathbf{k}\alpha}$ denotes the energy dispersions of the tight-binding bands calculated as follows: $t_{\mathbf{k}\alpha} = -\epsilon_0 - 2t_x \cos k_x - 2t_y \cos k_y + 4t' \cos k_x \cos k_y$. In accordance with experimental measurements of the Fermi surface and energy dispersions we choose the values for the parameter set $(\epsilon_0, t_x, t_y, t')$ as $(0.5, 0.42, 0.44, 0.14)$, $(0.23, 0.31, 0.055, 0.01)$, and $(0.24, 0.045, 0.31, 0.01)\text{eV}$ for d_{xy} -, d_{zx} -, and d_{yz} -orbitals [13]. The analysis of de Haas-van Alphen experiments [14] shows a substantial hybridization between xz - and

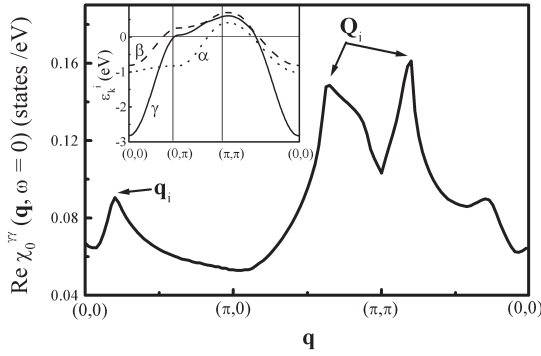


FIG. 1. Calculated susceptibility $\text{Re } \chi_0^{\gamma\gamma}(\mathbf{q}, \omega = 0)$ obtained from electronic calculations using the hybridized bands. The wave vectors $\mathbf{Q}_i = (\frac{2\pi}{3}, \frac{2\pi}{3})$ and $\mathbf{q}_i \approx (0.2\pi, 0)$ reflect nesting transferred from α and β bands and the original tendency of the γ band towards ferromagnetism, respectively. These wave vectors play the most important role for Cooper-pairing. The inset shows results for the energies ϵ_k^i of the hybridized bands ($i = \alpha, \beta, \gamma$).

yz - orbitals about $t_\perp = 0.1$ eV, but not with the xy -orbital [15]. However, the observation of a single T_c implies the coupling between all three bands. Therefore, we choose a weak hybridization $t_{hyb} = 0.01$ eV (hybridization between xy - and xz, yz -orbitals) $\ll t_\perp$. Note, even such a weak hybridization transfers the nesting properties to the xy -orbital. In the inset of Fig. 1 we show the resultant energy dispersions of the obtained hole-like α -band and electron-like β - and γ -bands after hybridization. Due to the small value of hybridization between xy and yz, xz orbitals the dispersion curves and resulting FS (see also Fig. 4) look quite similar to the non-hybridized ones [16]. However, the importance of hybridization between these orbitals for the spin susceptibility, $\chi(\mathbf{q}, \omega)$, will be immediately seen from the analysis of the latter. The susceptibility is given by:

$$\chi_0^{ij}(\mathbf{q}, \omega) = \frac{1}{N} \sum_{\mathbf{k}} \frac{f(\epsilon_{\mathbf{k}, \gamma}^i) - f(\epsilon_{\mathbf{k}+\mathbf{q}, \gamma}^j)}{\epsilon_{\mathbf{k}+\mathbf{q}, \gamma}^j - \epsilon_{\mathbf{k}, \gamma}^i + \omega + i0^+}, \quad (2)$$

where $f(\epsilon)$ is the Fermi function and ϵ_k^i is the energy dispersion of the α, β , and γ band [17].

In Fig. 1 we show the momentum dependence of the real part of $\chi_0^{\gamma\gamma}$. While hybridization between bands does not affect much the energy dispersion, it changes significantly the susceptibility of the γ -band. In particular, the nesting properties of xz - and yz -orbitals reflected by the peak at $\mathbf{Q}_i = (2\pi/3, 2\pi/3)$ in $\chi_0^{\gamma\gamma}$ are caused by the hybridization between xz, yz and xy bands. Note, without taking into account the hybridization one would not get the peak at $\mathbf{Q}_i$ in the γ -band, but only a broad hump as discussed earlier [16]. The small peak at $\mathbf{q}_i \approx (0.2\pi, 0)$ is due to the original tendency towards ferromagnetism of the xy -band and is not affected by the hybridization.

Our results for $\chi(\mathbf{q}, \omega)$ will have important consequences and were obtained in contrast to previous studies from observed band dispersions. The susceptibility matrix $[\chi^{ij}]$ is calculated where i, j refers to the hybridized

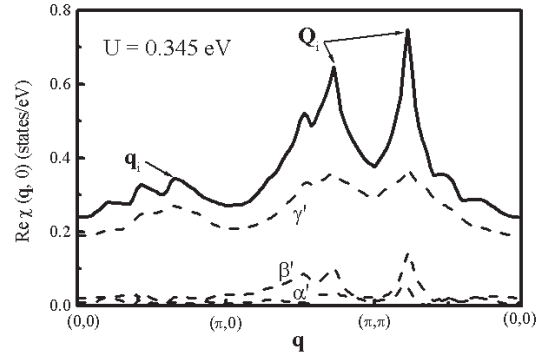


FIG. 2. Results are shown for the static susceptibility at $T = 50$ K. The solid curve refers to the total susceptibility within RPA resulting from the partial susceptibilities $\text{Re } \chi_0^{i'}(\mathbf{q}, \omega = 0)$ ($i' = \alpha', \beta', \gamma'$) shown by the dashed curves. The $\chi_0^{i'}$ refer to the diagonal elements of the diagonalized matrix $[\chi_0^{ij}]$. Note, the pairing wave vectors ($\mathbf{Q}_i, \mathbf{q}_i$) are nearly the same as in Fig. 1. Note, the smallness of $\chi_0^{\alpha'}$ and $\chi_0^{\beta'}$ as compared to $\chi_0^{\gamma'}$.

bands. As already mentioned the non-diagonalized susceptibilities are not small and thus cannot be neglected. After diagonalizing the matrix $[\chi_0^{ij}]$ we get within RPA with an effective $U(\mathbf{q})$ for χ :

$$\chi(\mathbf{q}, \omega) = \frac{\chi_0(\mathbf{q}, \omega)}{1 - U(\mathbf{q})\chi_0(\mathbf{q}, \omega)}, \quad (3)$$

where now $\chi_0(\mathbf{q}, \omega) = \sum_{i'} \chi_0^{i'}(\mathbf{q}, \omega)$. Here, $\chi_0^{i'}(\mathbf{q}, \omega)$ ($i' = \alpha', \beta', \gamma'$) are the diagonal elements of the diagonalized matrix $[\chi_0^{ij}]$. This obtained susceptibility characterizes the normal state magnetic properties of Sr_2RuO_4 . Its spin fluctuations are given by $\chi(\mathbf{q}, \omega)$ with peaks at $\mathbf{Q}_i$ and $\mathbf{q}_i$. These wave vectors are important for determining the symmetry of the superconducting order parameter.

In Fig. 2 we present the results for $\chi(\mathbf{q}, \omega)$ obtained from Eq. (3) and the susceptibilities $\chi_0^{i'}(\mathbf{q}, \omega)$ obtained after diagonalization of $[\chi_0^{ij}(\mathbf{q}, \omega)]$. Here, we approximate $U(\mathbf{q})$ by $U = 0.345$ eV which gives agreement with INS [18]. Remarkably, the peak in $\text{Re } \chi$ at $\mathbf{Q}_i$ remains nearly the same as for $\chi_0^{\gamma\gamma}$. The peak at $\mathbf{q}_i$ is also present, but slightly shifted to a larger value. Clearly, $\chi_0^{\gamma'}$ is much larger than $\chi_0^{\alpha'}$ and $\chi_0^{\beta'}$. Our calculations also have shown that cross-susceptibilities χ_0^{ij} ($i \neq j$) cannot be neglected.

In Fig. 3(a) we compare our calculation of the temperature dependence of the uniform spin susceptibility $\chi(0, 0)$ which is measured by the ^{17}O Knight shift [3], and in Fig. 3(b) we compare $\text{Im } \chi(\mathbf{Q}_i, \omega)$ with INS data [2]. For the calculation of $\chi(0, 0)$ we approximate $U(\mathbf{q})$ by $U(0) = 0.177$ eV [19] which gives agreement with Knight shift measurements and is also taken in previous calculations. These comparisons shed light on the validity of our results for $\chi(\mathbf{q}, \omega)$. Note, we also take into account that there are four electrons per three t_{2g} -bands that would give every $\chi_0^{i'}$ an additional weight $4/3$. Our results are in

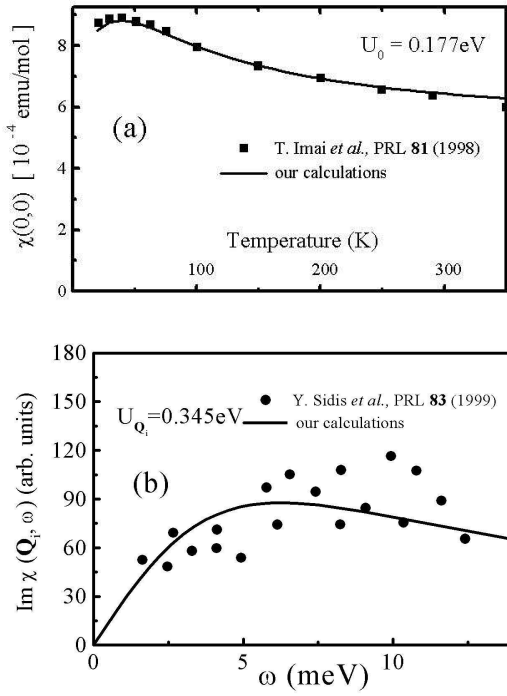


FIG. 3. (a) Calculated temperature dependence of the uniform spin susceptibility with $U_0=0.177\text{eV}$ is compared with the ^{17}O Knight shift measurements. The peak is due to thermal activation involving γ and α, β bands. (b) Calculated frequency dependence of $\text{Im } \chi(\mathbf{Q}_i, \omega)$ compared to INS data using $U_{\mathbf{Q}_i} = 0.345\text{eV}$.

fair agreement with experiment that shows a tendency towards ferromagnetism [20]. The maximum in $\chi_{RPA}(0,0)$ at about 25K results from thermally activated changes in the populations of the bands near E_F . In Fig. 3(b) we compare our results with INS data. In this case we must take $U_{\mathbf{Q}_i} = 0.345\text{eV}$ in order to fit $\chi(\mathbf{q}, \omega)$ to the peak position and height at $\omega=6\text{meV}$ as observed in INS.

While an uncertainty in the INS data (shown in Fig. 3(b)) is present, our results for $\chi(\mathbf{q}, \omega)$ should be a useful basis for further calculations. The antiferromagnetic spin excitations result in incommensurate antiferromagnetic Ru-spin alignment at distances larger than nearest neighbors. Hence, if Cooper-pairing involves nearest neighboring Ru spins also incommensurate antiferromagnetic fluctuations will cause triplet-pairing because neighboring Ru spins see also partly a *ferromagnetic* environment. Note, $\chi(\mathbf{q}, \omega)$ controls the symmetry of the superconducting order parameter.

For the analysis of superconductivity in Sr_2RuO_4 we take into account that experiment observes non-*s*-wave symmetry of the order parameter which strongly suggests spin-fluctuation-mediated Cooper pairing. Assuming the spin-fluctuation-induced pairing it is possible to analyze the symmetry of the superconducting state from the gap equation and our calculated results for $\chi(\mathbf{q}, \omega)$ with the pronounced wave vectors at $\mathbf{Q}_i$ and $\mathbf{q}_i$. We get for the gap equation:

$$\Delta_{\mathbf{k}}^i = - \sum_{\mathbf{k}', j} [V_{\sigma}^{eff}(\mathbf{k}, \mathbf{k}')]^{ij} \frac{\Delta_{\mathbf{k}'}^j}{2E_{\mathbf{k}'}^j} \tanh\left(\frac{E_{\mathbf{k}'}^j}{2k_B T}\right) \quad , \quad (4)$$

where $E_{\mathbf{k}}^i = \sqrt{\epsilon_{\mathbf{k}}^i{}^2 + \Delta_{\mathbf{k}}^2}$ are the energy dispersions of the bands [21] and the pairing potential $V_{\sigma}^{eff}(\mathbf{k}, \mathbf{k}')$ is different for singlet ($\sigma = 0$) and triplet ($\sigma = 1$) Cooper pairing. The eigenvalue analysis of Eq. (4) will yield the symmetry with lowest energy. The γ -band plays the most important role.

For the determination of the pairing symmetry we follow the analysis by Anderson and Brinkmann for ^3He [23] and by Scalapino for the cuprates [24] and use the calculated FS and spin susceptibility for Sr_2RuO_4 . For triplet pairing the effective pairing interaction is ($U \equiv U(\mathbf{Q}_i)$)

$$V_1^{eff}(\mathbf{k}, \mathbf{k}') = - \frac{U^2 \chi_0(\mathbf{k} - \mathbf{k}', 0)}{1 - U^2 \chi_0^2(\mathbf{k} - \mathbf{k}', 0)} = - \frac{U^2}{2} \left(\frac{\chi_0(\mathbf{k} - \mathbf{k}', 0)}{1 - U \chi_0(\mathbf{k} - \mathbf{k}', 0)} + \frac{\chi_0(\mathbf{k} - \mathbf{k}', 0)}{1 + U \chi_0(\mathbf{k} - \mathbf{k}', 0)} \right) \quad , \quad (5)$$

and for singlet pairing

$$V_0^{eff}(\mathbf{k}, \mathbf{k}') = \frac{U^2 \chi_0(\mathbf{k} - \mathbf{k}', 0)}{1 - U \chi_0(\mathbf{k} - \mathbf{k}', 0)} + \frac{U^3 \chi_0^2(\mathbf{k} - \mathbf{k}', 0)}{1 - U^2 \chi_0^2(\mathbf{k} - \mathbf{k}', 0)} \quad , \quad (6)$$

respectively [25]. It is important to note that for $E_F \gg \Delta_l$ the gap function can be expanded into spherical harmonics corresponding to the angular momentum $l = 1, 2, 3, \dots$ and no mixture of Δ_l belonging to different symmetry representations can be present if a single T_c is observed. Therefore, we can exclude the ($p + d$)-wave superconducting state. Using appropriate symmetry representations [8] we discuss the solutions of Eq. (4) for the p , d , and f -wave symmetries of the order parameter:

$$\Delta_p(\mathbf{k}) = \Delta_0 \hat{\mathbf{z}} (\sin k_x + i \sin k_y), \quad (7)$$

$$\Delta_d(\mathbf{k}) = \Delta_0 (\cos k_x - \cos k_y), \quad (8)$$

$$\Delta_f(\mathbf{k}) = \Delta_0 \hat{\mathbf{z}} (\cos k_x - \cos k_y) (\sin k_x + i \sin k_y). \quad (9)$$

Note, the largest eigenvalue in Eq. (4) will yield the superconducting symmetry of Δ_l in Sr_2RuO_4 . Solving Eq. (4) in the first BZ down to 5K, we find f -wave symmetry slightly favored. As expected p - and f -wave symmetry Cooper-pairing are close in energy ($\lambda_f = 0.76 > \lambda_p = 0.51$). A more complete analysis taking into account also the coupling between RuO_2 planes and interband U might yield a definite answer [22]. Note, to obtain a combined energy gain from the antiferromagnetism and Cooper-pairing one expects an order parameter with nodes in the RuO_2 plane and possibly also with respect to the c -direction.

The solutions of Eq. (4) can be characterized by Fig. 4 where we present our results for the Fermi surface, wave

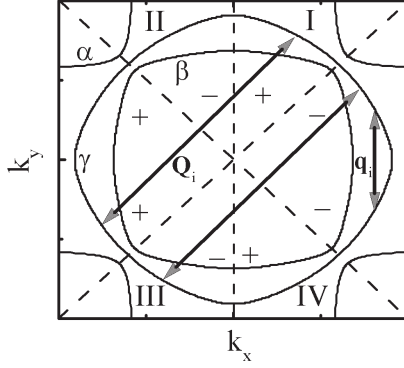


FIG. 4. Symmetry analysis of the order parameter for the triplet pairing in the first BZ. α , β , and γ denote the FS of the corresponding hybridized bands. The wave vectors $\mathbf{Q}_i$ and $\mathbf{q}_i$ are the pronounced wave vectors resulting from the susceptibility shown in Fig. 2. These determine the symmetry of the order parameter. Also for f -wave symmetry the nodes of the real part of the order parameter are shown (dashed lines) and the regions + (-) where the f -wave superconducting gap is positive (negative). Note, for the real part of the p -wave order parameter the node occurs along $k_x=0$.

vectors $\mathbf{Q}_i$ and $\mathbf{q}_i$ and symmetry of the order parameter in Sr_2RuO_4 . The areas with $\Delta_f > 0$ and $\Delta_f < 0$ are denoted by (+) and (-), respectively. In a good approximation we linearize Eq. (4) in Δ_l , i.e. $E_{\mathbf{k}'}^{\gamma} \rightarrow \epsilon_{\mathbf{k}'}^{\gamma}$, and safely put $\tanh(\epsilon_{\mathbf{k}'}^{\gamma}/2k_B T) = 1$. Therefore, the main contribution to the pairing comes from the Fermi level. Note, determining Δ_l for the RuO_2 -planes it is sufficient to take into account only the γ -band, since only this band has a dispersion in the plane. The minus sign in Eq. (4) is cancelled for triplet pairing (see Eq. (5)). Furthermore, the summation over $\mathbf{k}'$ in the first BZ is dominated by the contributions due to $\mathbf{Q}_i$ and the one due to the background and $\mathbf{q}_i$. Thus, we obtain approximately for the γ -band contribution ($l = f$ or p)

$$\Delta_l(\mathbf{k}) \approx \sum_i \frac{V_1^{eff}(\mathbf{Q}_i)}{2\epsilon_{\mathbf{k}+\mathbf{Q}_i}^{\gamma}} \Delta_l(\mathbf{k} + \mathbf{Q}_i) + \sum_i \frac{V_1^{eff}(\mathbf{q}_i)}{2\epsilon_{\mathbf{k}+\mathbf{q}_i}^{\gamma}} \Delta_l(\mathbf{k} + \mathbf{q}_i) , \quad (10)$$

where the sum is over all contributions due to $\mathbf{Q}_i$ and $\mathbf{q}_i$. As can be seen from Fig. 4 in the case of f -wave symmetry the wave vector $\mathbf{q}_i$ in Eq. (10) bridges the same number of portions of the FS with opposite and equal sign. Therefore, the second term in Eq. (10) is approximately zero for triplet pairing. We see from Fig. 4 that $\mathbf{Q}_i$ bridges portions of the FS with *equal* signs of the superconducting order parameter. Thus, a solution of Eq. (10) for Δ_f is indeed possible.

In the case of p -wave pairing the real part of the order parameter has a node only along $k_x = 0$ in the k_x, k_y -plane. Then, using the corresponding Fig. 4 the wave vectors $\mathbf{Q}_i$ bridge portion of the FS where $\text{Re}\Delta_p$ has the

same or opposite sign. Regarding the $\mathbf{q}_i$ contributions the situation is similar as in the case of the f -wave symmetry. Hence, we expect for the eigenvalues $\lambda_p \leq \lambda_f$ as in the result of the algebraic solution of Eq. (4). Note, for increasing nesting Fig. 4 also suggests that f -wave symmetry is favored more than p -wave. The eigenvalue analysis of the possible solutions Δ_f and $\Delta_p + i\Delta_f$ should increasingly rule out the latter for stronger nesting

Also using similar arguments we can rule out singulet pairing on the basis of Eq. (6). In particular, assuming $d_{x^2-y^2}$ -symmetry for Sr_2RuO_4 we get a change of sign of the order parameter upon crossing the diagonals of the BZ. According to Eq. (4) wave vectors around $\mathbf{Q}_i$ connecting areas (+) and (-) contribute constructively to the pairing. Contributions due to $\mathbf{q}_i$ and the background connecting the same sign areas subtract from the pairing (see Fig. 4 with nodes at the diagonals for illustration). Therefore, we get that the four contributions due to $\mathbf{q}_i$ and the background cancel the pair-building contribution due to $\mathbf{Q}_i$. As a consequence we obtain no $d_{x^2-y^2}$ -wave symmetry. Note, this is in contrast to the cuprates where the cancelling contributions due to $\mathbf{q}_i$ and the small background are negligible. For the d_{xy} -symmetry where the nodes are along $(\pi, 0)$ and $(0, \pi)$ directions we can argue similarly and thus exclude this symmetry.

Thus, as a result of the topology of the FS and the spin susceptibility we get for p - and f -wave the strongest pairing and can definitely exclude d -wave pairing. In our approximation we find that f -wave symmetry pairing is slightly favored over p -wave symmetry in Sr_2RuO_4 .

In view of our Fig. 4 we also remark that while $\text{Re}\Delta_f$ exhibits three line nodes, that can be seen by phase sensitive experiments, $|\Delta_f|^2$ shows nodes only along the diagonals, as recently found in measurements of ultrasound attenuation below T_c [26]. However, note in view of the low eigenvalues for p and f -wave symmetries and approximations used we cannot definitely conclude that f -wave is favored over p -wave.

In summary, we show that hybridization between all three bands is important and transfers the nesting properties of xz - and yz -orbitals to the γ band in Sr_2RuO_4 . Taking into account all cross-susceptibilities we successfully explain the ^{17}O Knight shift and INS data. Most importantly, we calculate $\chi(\mathbf{q}, \omega)$ and show on the basis of the Fermi surface topology and the calculated spin susceptibility $\chi(\mathbf{q}, \omega)$ that triplet pairing is present in Sr_2RuO_4 . Our analysis seems quite general and also predicts d -wave symmetry for electron- and hole-doped cuprates [27]. To decide whether p - or f -wave symmetry pairing is present one needs to perform more complete calculations including coupling between RuO_2 planes, for example. If the interplane coupling involves also nesting, then corresponding nodes are expected.

We are thankful for stimulating discussions with P. Thalmeier, M. Sigrist, R. Klemm, M. Kagan, and D. Agterberg. I.E. is supported by Alexander von Hum-

-
- [1] Y. Maeno *et al.*, Nature **372**, 532 (1994); Y. Maeno, T.M. Rice, and M. Sigrist, Phys. Today, No. 1, 42 (2001).
- [2] Y. Sidis *et al.*, Phys. Rev. Lett. **83**, 3320 (1999).
- [3] T. Imai *et al.*, Phys. Rev. Lett. **81**, 3006 (1998); K. Ishida *et al.*, Phys. Rev. **B 64**, 100501 (2001).
- [4] K. Ishida *et al.*, Phys. Rev. **B 56**, R505 (1997).
- [5] J.A. Duffy *et al.*, Phys. Rev. Lett. **85**, 5412 (2000).
- [6] M. Sigrist *et al.*, Physica **C 317-318**, 134 (1999); D.F. Agterberg, T.M. Rice, and M. Sigrist, Phys. Rev. Lett. **78**, 3374 (1997); L. Tewordt, Phys. Rev. Lett. **83**, 1007 (1999).
- [7] T. Dahm, H. Won, and K. Maki, preprint cond-mat/0006301.
- [8] Y. Hasegawa, K. Machida, and M. Ozaki, J. Phys. Soc. Jpn. **69**, 336 (2000).
- [9] K. Izawa *et al.*, Phys. Rev. Lett. **86**, 2653 (2001); M.A. Tanatar *et al.*, Phys. Rev. Lett. **86**, 2649 (2001).
- [10] I.I. Mazin and D.J. Singh, Phys. Rev. Lett. **82**, 4324 (1999).
- [11] K. Kuroki *et al.*, Phys. Rev. **B 63**, 060506(R) (2001).
- [12] T. Kuwabara and M. Ogata, Phys. Rev. Lett. **85**, 4586 (2000).
- [13] A. Damascelli *et al.*, Phys. Rev. Lett. **85**, 5194 (2000).
- [14] A.P. Mackenzie *et al.*, Phys. Rev. Lett. **76**, 3786 (1996).
- [15] D. K. Morr, P. F. Trautmann, and M. J. Graf, Phys. Rev. Lett. **86**, 5978 (2001).
- [16] T. Takimoto, Phys. Rev. **B 62**, R14641 (2000).
- [17] We also include the matrix element for the spin susceptibility χ_0^{ij} taken to be 1 between two states which have the same maximal character and 0 otherwise in accordance with Ref. [10].
- [18] While the exact $\mathbf{q}$ -dependence of U is unknown it is reasonable to assume that $U(\mathbf{q})$ increases with $\mathbf{q}$. Thus to fit the peak at $\mathbf{q}=\mathbf{Q}_i$ to INS one may need $U(\mathbf{Q}_i) > U(0)$, where $U(0)$ refers to $\chi(0,0)$.
- [19] A. Liebsch, and A. Lichtenstein, Phys. Rev. Lett. **84**, 1591 (2000).
- [20] In the original paper [3] the effect of cross-susceptibilities was not considered. Therefore, we compare our results to the total susceptibility $\chi_{xy} + \chi_{yz} + \chi_{xz}$.
- [21] Since γ -band contains the information about the nesting properties of the α - and β -bands and due to the neglect of the interband Coulomb interaction, we solve the gap equation only for the leading γ -band and taking into account the full pairing potential obtained from the diagonalizing of the $[\chi^{ij}]$ matrix.
- [22] If the energy difference between p - and f -wave symmetry in the RuO_2 planes is larger than the energy gain for superconductivity resulting from interplane coupling, one may determine the pairing symmetry from the in-plane electronic structure.
- [23] A.J. Layzer and D. Fay, *Proc. Int. Low Temp. Conf.*, St. Andrews (LT-11), Academic Press, London, (1968); P.W. Anderson and W.F. Brinkmann, in "The physics of liquid and solid Helium", eds. K.H. Bennemann and J.B. Ketterson (V. 2, Wiley-Interscience Publication, 1978).
- [24] N.F. Berk and J.R. Schrieffer, Phys. Rev. Lett. **17**, 433 (1966); D.J. Scalapino, Phys. Rep. **250**, 329 (1995).
- [25] Note, the second term in V_0 comes from ladder diagrams which do not contribute to the triplet pairing due to the Pauli principle.
- [26] C. Lupien *et al.*, Phys. Rev. Lett. **86**, 5986 (2001).
- [27] D. Manske, I. Eremin, and K.H. Bennemann, Phys. Rev. **B 62**, 13922 (2000).